arXiv:1402.5220v1 [cond-mat.supr-con] 21 Feb 2014

Enhancement of Superconducting Transition Temperature Due to Antiferromagnetic Spin Fluctuations in Iron-pnictides $LaFe(As_{1-x}P_x)(O_{1-y}F_y)$: ^{31}P-NMR Studies

H. Mukuda,[1,*] F. Engetsu,[1] K. Yamamoto,[1] K. T. Lai,[2] M. Yashima,[1] Y. Kitaoka,[1]
A. Takemori,[2] S. Miyasaka,[2] and S. Tajima[2]

[1]*Graduate School of Engineering Science, Osaka University, Osaka 560-8531, Japan*
[2]*Graduate school of Science, Osaka University, Osaka 560-0043, Japan*

(Dated: February 24, 2014)

Systematic ^{31}P-NMR studies on $LaFe(As_{1-x}P_x)(O_{1-y}F_y)$ with y=0.05 and 0.1 have revealed that the antiferromagnetic spin fluctuations (AFMSFs) at low energies are markedly enhanced around x=0.6 and 0.4, respectively, and as a result, T_c exhibits respective peaks at 24 and 27 K against the P substitution for As. This result demonstrates that the AFMSFs are responsible for the increase in T_c for $LaFe(As_{1-x}P_x)(O_{1-y}F_y)$ as a primary mediator of the Cooper pairing. From a systematic comparison of AFMSFs with a series of $(La_{1-z}Y_z)FeAsO_\delta$ compounds in which T_c reaches 50 K for z=0.95, we remark that a moderate development of AFMSFs causes T_c to increase up to 50 K under the condition that the local lattice parameters of the FeAs tetrahedron approach those of the regular tetrahedron. We propose that T_c of Fe-pnictides exceeding 50 K is maximized under an intimate collaboration of the AFMSFs and other factors originating from the optimization of the local structure.

I. INTRODUCTION

The iron-based oxypnictide LaFeAsO, which is an antiferromagnet with an orthorhombic structure, becomes a superconductor at transition temperature T_c=26 K for $LaFeAsO_{1-y}F_y$(La1111) by the substitution of O^{2-} with F^- when y=0.1[1,2]. Since its discovery, the role of antiferromagnetic spin fluctuations (AFMSFs) is believed to be indispensable for the onset of superconductivity (SC). On the other hand, it was reported that T_c reaches a maximum of 55 K for the Sm1111 compound[3,4], in which the $FeAs_4$ block forms into a nearly regular tetrahedral structure[5]. In this structure, the optimal values for the lattice parameters, which enhance T_c, are the As-Fe-As bonding angle α=109.5°[5], the height of the pnictogen h_{Pn} ∼1.38Å from the Fe plane[6], and the a-axis length a ∼3.9Å[4,7]. This regular tetrahedral structure is expected to yield a multiplicity of the Fermi surface topology, multiple excitations that are relevant to the d-orbital degeneracy, and fluctuations of d orbital and spin degrees of freedom.

In order to shed further light on an interplay between AFMSFs and fluctuations originating from the local degrees of freedom, we present normal-state and SC characteristics probed by a ^{31}P-NMR for a series of $LaFe(As_{1-x}P_x)(O_{1-y}F_y)$ compounds with y=0.1 and 0.05. The isostructural compound LaFePO exhibits an SC transition at T_c ∼ 4 K without any substitution, however, a partial replacement of O^{2-} with F^- causes T_c to increase to 7 K[8]. In $LaFe(As_{1-x}P_x)(O_{0.9}F_{0.1})$, which are all superconductive[9,10], T_c reaches a maximum of 27 K at x=0.4 as shown in Fig. 1, even though the lattice parameters are monotonously varied with x and are apart from the optimum values of the $FeAs_4$ block[9,11]. In this context, further systematic studies on these $LaFe(As_{1-x}P_x)(O_{1-y}F_y)$ compounds provide us with an opportunity to identify a possible parameter for raising the T_c, apart from the optimization of the local structure of the Fe-based superconductors. In fact, here we report that as a consequence of the development of the AFMSFs at low energies for compounds at x=0.4 and y=0.1, the T_c increases to 27 K, which is higher than the T_c for the original compound at x=0 and y=0.1. However, when AFMSFs are not visible, the T_c at x=1.0 decreases to 5.4 K. Similar results have been obtained for the underdoped compounds at y=0.05. Present studies reveal that the AFMSFs are indispensable for raising the T_c in $LaFe(As_{1-x}P_x)(O_{1-y}F_y)$ compounds.

II. EXPERIMENT

Polycrystalline samples of $LaFe(As_{1-x}P_x)(O_{1-y}F_y)$ were synthesized by the solid-state reaction method, as described elsewhere[9,11]. Powder X-ray diffraction measurements indicate that these samples are comprised of a single phase. Bulk T_cs were determined from an onset of SC diamagnetism in the susceptibility measurement. As shown in Fig. 1, the T_c exhibits a maximum at x=0.4 for y=0.1[9,10], however, they exhibit a shallow minimum around x=0.3∼0.4 and a local maximum at x=0.6 for y=0.05[11]. ^{31}P-NMR(I = 1/2) measurements on these compounds have been performed on coarse powder samples with a nominal content of x=0.4(T_c=27 K), x=0.8(T_c=8.8 K), and x=1.0(T_c=5.4 K) for y=0.1, and x=0.4(T_c=19 K), x=0.6(T_c=24 K) and x=1.0(T_c=6.7 K) for y=0.05, as indicated by the arrows in Fig. 1. The respective values of a-axis length, h_{Pn}, and α in $LaFe(As_{1-x}P_x)(O_{1-y}F_y)$ monotonously vary from 4.002Å, 1.24Å, and 116.3° for x=0.4 to 3.951Å, 1.15Å, and 119.7° for x=1.0 when y=0.1, and from 4.011Å, 1.25Å, and 116.0° for x=0.4 to 3.959Å, 1.12Å, and 121.1° for x=1.0 when y=0.05[9,11].

The ^{31}P-NMR Knight shift ^{31}K was measured under a

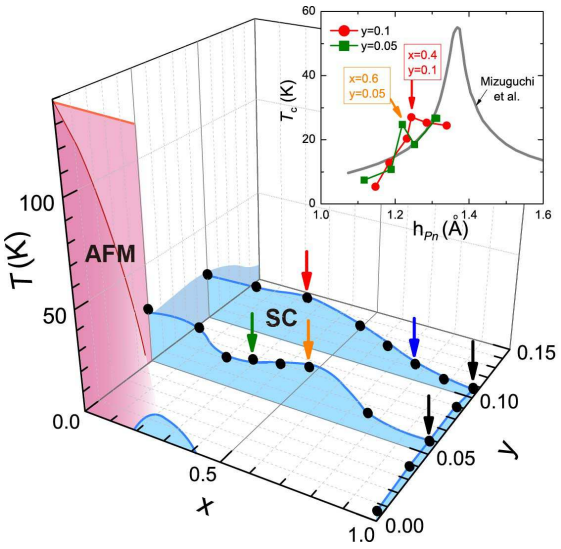

FIG. 1: (Color online) Phase diagram of $LaFe(As_{1-x}P_x)(O_{1-y}F_y)$. The T_c and T_N values come from the previous works on $LaFe(As_{1-x}P_x)(O_{0.9}F_{0.1})$[9–11], $LaFe(As_{1-x}P_x)O$[12], $LaFeP(O_{1-y}F_y)$[13], and $LaFeAs(O_{1-y}F_y)$[1,2]. The arrows indicate the content for the samples used here. The inset shows T_c vs h_{Pn} for $LaFe(As_{1-x}P_x)(O_{1-y}F_y)$ plotted on a universal relation for many Fe-pnictides reported by Mizuguchi *et al.*[6].

magnetic field of ∼11.95 T, which was calibrated by a resonance field of ^{31}P in H_3PO_4. The nuclear-spin-lattice-relaxation rate $^{31}(1/T_1)$ of ^{31}P-NMR was obtained by fitting a recovery curve of ^{31}P nuclear magnetization to a single exponential function $m(t) \equiv (M_0 - M(t))/M_0 = \exp(-t/T_1)$. Here, M_0 and $M(t)$ are the nuclear magnetizations for a thermal equilibrium condition and at time t after the saturation pulse, respectively. Note, however, that $m(t)$ in some compounds includes two components in $1/T_1$, as shown in the inset of Figs. 2(c) and 5(c), due to some inevitable inhomogeneity of the electronic states in association with the chemical substitution of P for As. Here, since the fraction of the short component of $1/T_1$ was predominantly larger than the long one, $1/T_1$ was determined by the short component.

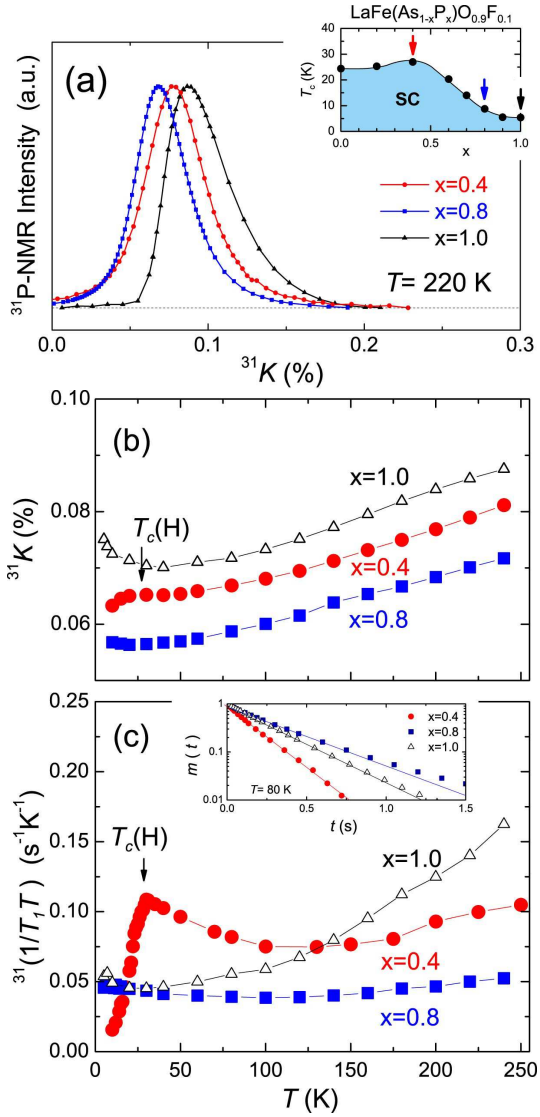

FIG. 2: (Color online) (a) ^{31}P-NMR spectra at T=220 K, and T dependence of the (b) Knight shift (^{31}K) and (c) $^{31}(1/T_1T)$ for $LaFe(As_{1-x}P_x)(O_{0.9}F_{0.1})$. The arrows in the inset of (a) indicate the samples used in this experiment. $T_c(H)$ indicates T_c under the field H ∼11.95 T. The inset in (c) shows the typical recovery curves of the nuclear magnetization to determine $1/T_1$.

III. RESULTS

A. $LaFe(As_{1-x}P_x)(O_{0.9}F_{0.1})$

Figure 2(a) shows the ^{31}P-NMR spectra at T= 220 K for x=0.4, 0.8, and 1.0 of $LaFe(As_{1-x}P_x)(O_{0.9}F_{0.1})$. The full-width at half maximum (FWHM) of the ^{31}P-NMR spectra is quite narrow, for example, ∼90(∼79) kHz at x=0.4 (x=0.8) at the resonance frequency ∼206 MHz. Figures 2(b) and 2(c) show the T dependence of Knight shift (^{31}K) and $^{31}(1/T_1T)$, respectively, for x=0.4, 0.8, and 1.0 of $LaFe(As_{1-x}P_x)(O_{0.9}F_{0.1})$. Both the ^{31}K and $^{31}(1/T_1T)$ gradually decrease upon cooling at high temperatures, in contrast to that at low temperatures where the T dependence of $^{31}(1/T_1T)$ strongly depends on the x.

The Knight shift comprises the T-dependent spin shift $^{31}K_s(T)$ and the T-independent chemical shift $^{31}K_{chem}$. The former $^{31}K_s(T)$ is given using the static spin susceptibility $\chi(\boldsymbol{q}=0)$ by

$$K_s(T) \propto A_{q=0}\ \chi(\boldsymbol{q}=0) \propto A_{q=0}N(E_F),$$

where $A_{q=0}$ is the hyperfine-coupling constant for the q=0 wave number and $N(E_F)$ is the density of states (DOS) at the Fermi level (E_F). In the nonmagnetic com-

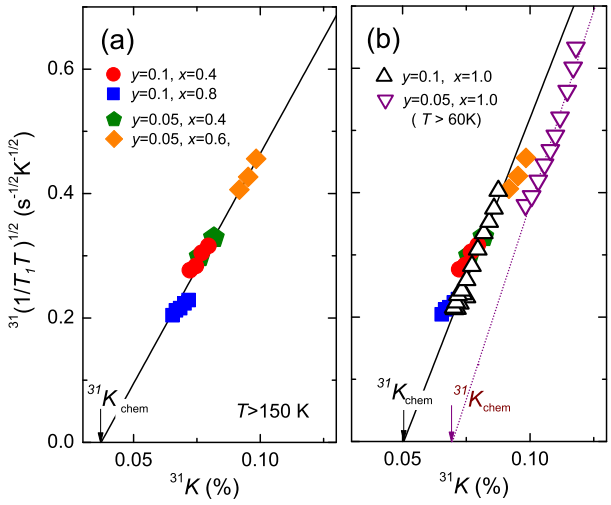

FIG. 3: (Color online) Plot of $^{31}(1/T_1T)^{1/2}$ vs. ^{31}K with an implicit parameter of T. (a) For x=0.4 and 0.8 at y=0.1 and x=0.4 and 0.6 at y=0.05, the T-independent $^{31}K_{chem}$ was evaluated to be 0.037% using the data of $T > 150$ K since the AFMSFs develop below 100 K. (b) For x=1.0, $^{31}K_{chem}$ was evaluated to be 0.05% in the T range of $T > 60$ K for y=0.05 and 0.07% in the whole T range for y=0.1.

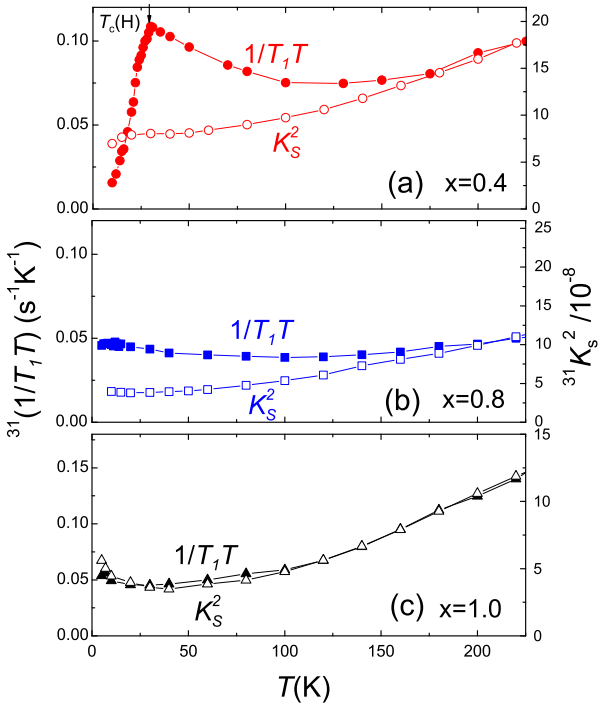

FIG. 4: (Color online) T dependence of $^{31}K_s^2$(=($^{31}K - ^{31}K_{chem}$)^2) and $^{31}(1/T_1T)$ for (a)x=0.4, (b) x=0.8, and (c) x=1.0 of LaFe(As$_{1-x}$P$_x$)(O$_{0.9}$F$_{0.1}$).

pounds, $^{31}K_s$ is proportional to $^{31}(1/T_1T)^{0.5}$ since Korringa's relation $^{31}(1/T_1T) \propto N(E_F)^2$ holds. As shown in Fig. 3, the plot of $^{31}(1/T_1T)^{0.5}$ and ^{31}K enables us to evaluate $^{31}K_{chem}$ to be ∼0.05% for x=1.0 using the data in whole T range and ∼0.037% for x=0.4 and 0.8 using the data at high temperatures (T >150 K), where the contribution of AFMSFs in $1/T_1T$ is negligible. The $^{31}K_s(T)$ that is evaluated from the relation of $^{31}K - ^{31}K_{chem}$ decreases as the temperature lowers, as is observed for most electron-doped compounds[14–17]. It is due to the narrow peak of the DOS being located below the E_F, which is the characteristic band structure for electron-doped systems[18]. In general, $1/T_1T$ can be expressed as

$$\frac{1}{T_1T} \propto \lim_{\omega_0 \to 0} \sum_{\boldsymbol{q}} |A_{\boldsymbol{q}}|^2 \frac{\chi''(\boldsymbol{q}, \omega_0)}{\omega_0},$$

where $A_{\boldsymbol{q}}$ is the $\boldsymbol{q}$-dependent hyperfine-coupling constant, $\chi(\boldsymbol{q}, \omega)$ is the dynamical spin susceptibility, and ω_0 is the NMR frequency. Note that $1/T_1T$ is dominated by spin fluctuations at the low-energy limit since the NMR frequency ω_0 is as low as a radio frequency. Figures 4(a), 4(b), 4(c) show the T dependence of $^{31}(1/T_1T)$ and $^{31}K_s^2$ for x=0.4, x=0.8, and x=1.0, respectively. $^{31}K_s(T)$, which is proportional to $\chi(\boldsymbol{q} = 0)$, decreases upon cooling, whereas $^{31}(1/T_1T)$ at x=0.4 increases up to $T_c(H)$ upon cooling below 100 K, indicating that the development of AFMSFs occurred at a finite Q wave vector presumably around ($\pm\pi$, 0) and (0, $\pm\pi$)[19]. By contrast, such an increase of $^{31}(1/T_1T)$ at low temperature is gradually suppressed at x=0.8 and considerably suppressed at x=1.0, where the decrease of $^{31}(1/T_1T)$ upon cooling is almost the same as that of $^{31}K_s^2$. The results demonstrate that strong AFMSFs at x=0.4 that exhibit higher T_c gradually decrease toward x=1.0 with lower T_c.

B. LaFe(As$_{1-x}$P$_x$)(O$_{0.95}$F$_{0.05}$)

Next, we show the results for the underdoped compounds of LaFe(As$_{1-x}$P$_x$)(O$_{0.95}$F$_{0.05}$), i.e. for x=0.4 with T_c=19 K, x=0.6 with T_c=24 K, and x=1.0 with T_c=6.7 K. The ^{31}P-NMR spectra for x=0.4, 0.6, and 1.0 are shown in Fig. 5(a). The FWHM is also as narrow as ∼73 (∼135) kHz at x=0.4 (0.6) at the resonance frequency ∼206 MHz. Figures 5(b) and 5(c) show the T dependence of the Knight shift ^{31}K and $^{31}(1/T_1T)$ for x=0.4, 0.6, and 1.0 of LaFe(As$_{1-x}$P$_x$)(O$_{0.95}$F$_{0.05}$). As indicated in Fig. 3, $^{31}K_{chem}$ is evaluated to be ∼0.037% for x=0.4 and 0.6 using the data at high temperatures and ∼0.07% for x=1.0 using the data in broad T range (T >60 K). Figures 6(a), 6(b) 6(c) indicate the T dependence of $^{31}K_s^2$ and $^{31}(1/T_1T)$ for x=0.4, x=0.6, and x=1.0, respectively. The $^{31}(1/T_1T)$ values increase upon cooling below 100 K for x=0.4 and 0.6, although $^{31}K_s$ for these compounds monotonously decreases with decreasing T. In particular, $^{31}(1/T_1T)$ is more enhanced at x=0.6 than at x=0.4 and 1.0, demonstrating that the AFMSFs develop more significantly for x=0.6 which exhibits the higher T_c than for x=0.4 and 1.0 with the lower T_c.

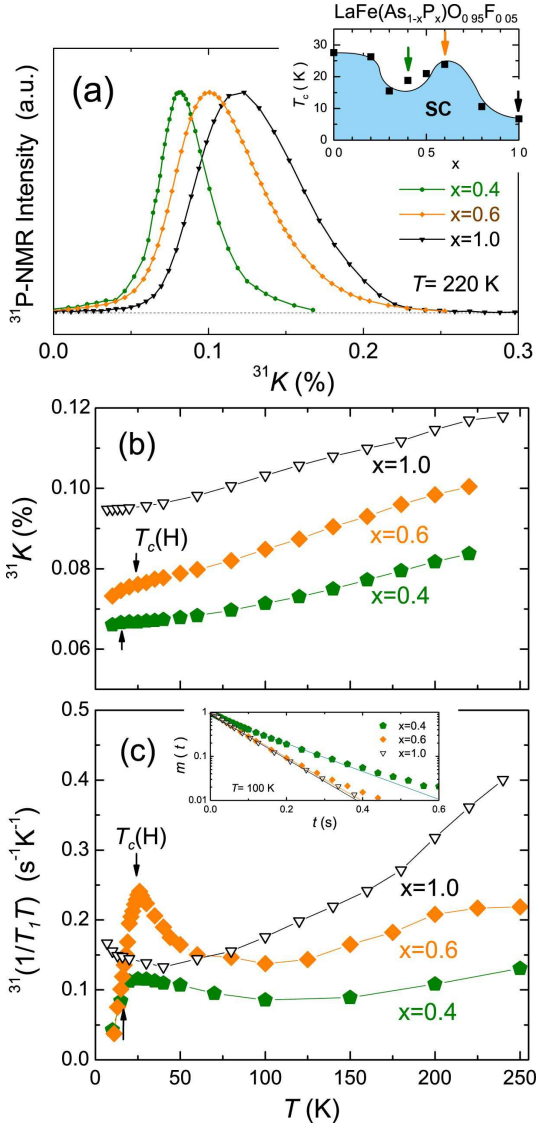

FIG. 5: (Color online) (a) ^{31}P-NMR spectra at T=220 K, and T dependence of the (b) Knight shift (^{31}K) and (c) $^{31}(1/T_1T)$ for LaFe(As$_{1-x}$P$_x$)(O$_{0.95}$F$_{0.05}$). The arrows in the inset of (a) indicate the samples used in this experiment. $T_c(H)$ indicates T_c under the field H ∼11.95 T. The inset in (c) shows the typical recovery curves to determine $1/T_1$.

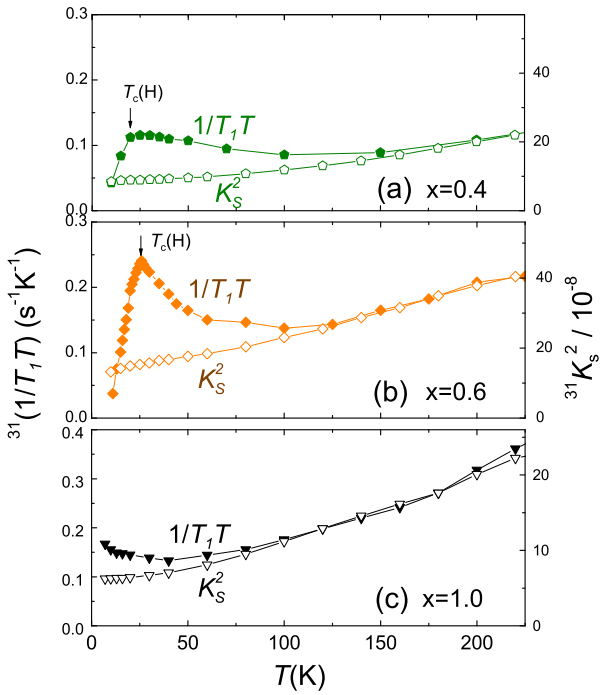

FIG. 6: (Color online) T dependence of $^{31}K_s^2$(= ($^{31}K - ^{31}K_{chem}$)^2) and $^{31}(1/T_1T)$ for (a)x=0.4, (b) x=0.6, and (c) x=1.0 of LaFe(As$_{1-x}$P$_x$)(O$_{0.95}$F$_{0.05}$).

C. AFM spin fluctuations in LaFe(As,P)(O,F)

Eventually, we remark that T_c increases as AFMSFs are further enhanced for LaFe(As$_{1-x}$P$_x$)(O$_{1-y}$F$_y$) compounds studied here. In order to deduce the development of AFM spin fluctuations for LaFe(As$_{1-x}$P$_x$)(O$_{1-y}$F$_y$), we assume that $^{31}(1/T_1T)$ is decomposed as,

$$^{31}(1/T_1T) = ^{31}(1/T_1T)_{Q(AF)} + ^{31}(1/T_1T)_{Q-indep},$$

where the former term represents the AFM spin fluctuations at finite Q presumably around (0,π) and (π,0) that significantly develop upon cooling, and the latter term represents the other q-independent part of the background. At high temperatures, the T dependence of $^{31}(1/T_1T)$ resembles $^{31}K_s^2(T)$, as shown in Figs. 4 and 6, implying that $^{31}(1/T_1T)_{Q-indep}$ is predominant at high temperatures. Then, we can evaluate the T dependence of $^{31}(1/T_1T)_{Q(AF)}$ by assuming that the T dependence of $^{31}(1/T_1T)_{Q-indep}$ is identical to that of $^{31}K_s^2(T)$. As a result, in Figs. 7(a) and 7(b) we show the contour plots of $^{31}(1/T_1T)_{Q(AF)}$ for y=0.05 and y=0.1, respectively. These results demonstrate that the AFMSFs develop significantly for x=0.6 at y=0.05 and x=0.4 at y=0.1, where T_c exhibits a peak against the variation of x. Namely, the AFMSFs play an important role in raising T_c in the LaFe(As,P)(O,F) series, although the local structure is apart from the optimum values of the Fe-based superconductors[5,6](see the inset of Fig. 1).

IV. DISCUSSION

In Fe-pnictide compounds such as Ba(Fe,Co)$_2$As$_2$[17], Fe(Se,Te)[16,20], BaFe$_2$(As,P)$_2$[21], and Na(Fe,Co)As[22], it has been well established that T_c exhibits a maximum close to the AFM phase in which AFMSFs are critically enhanced. On the other hand, for the LaFeAs(O$_{1-y}$F$_y$) series, the maximum T_c emerges at y=0.1 without any development of AFMSFs upon cooling down to T_c[14,15,23], although AFMSFs can be observed in the vicinity of the AFM ordered phase with a lower T_c, i.e., in the range of $0.04 < y < 0.08$[24–26]. In this context, we emphasize

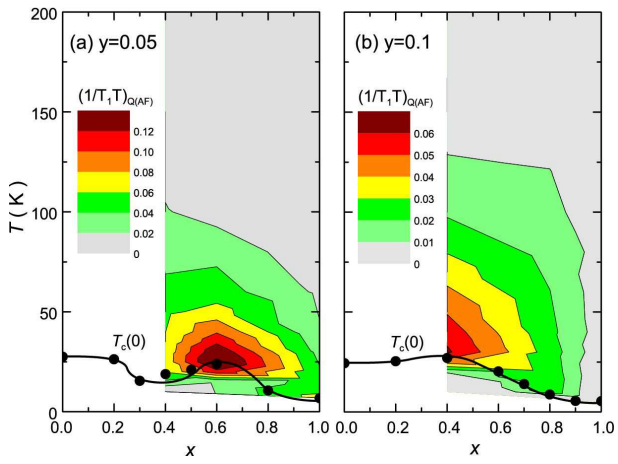

FIG. 7: (Color online) Contour plot of $^{31}(1/T_1T)_{Q(AF)}$ for (a)y=0.05 and (b) y=0.1, indicating the development of AFM spin fluctuations at finite Q wave vector is significant in the compounds, where $T_c(0)$ exhibits a peak against the variation of x. Here, $T_c(0)$ represents the T_c values at zero external field[9,11].

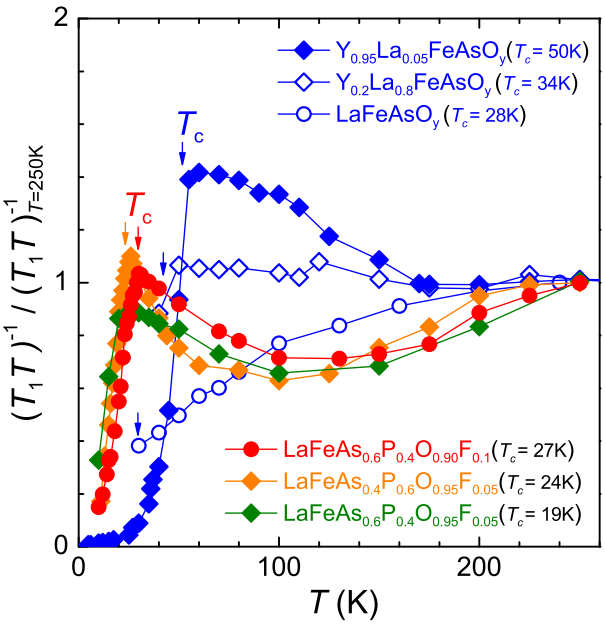

FIG. 8: (Color online) T dependence of $(T_1T)^{-1}/(T_1T)^{-1}_{T\sim250K}$ by means of ^{31}P-NMR for the present samples, which are compared with ^{75}As-NMR results for $Y_{0.95}La_{0.05}FeAsO_\delta$ (T_c=50 K)[27], $Y_{0.2}La_{0.8}FeAsO_\delta$ (T_c=34 K)[29], and $LaFeAsO_\delta$ (T_c=28 K)[30].

that the present studies of the LaFe(As,P)(O,F) compounds series provide clear evidence that the development of AFMSFs enhances T_c even if the present La1111 compounds are far away from the AFM ordered phase and optimal lattice parameters(see the inset of Fig. 1).

Finally, we discuss a systematic comparison of the spin fluctuations among the LaFeAsO(1111)-based family, as shown in Fig. 8. $Y_{0.95}La_{0.05}$1111 with T_c=50 K[27] possessing near-optimal structural parameters in the FeAs block ($h_{pn} \sim 1.44$Å) is characterized by three hole Fermi surfaces; two of them are located at Γ(0,0) and the other is at $\Gamma'(\pi,\pi)$, and two electron Fermi surfaces at $M[(0,\pi)(\pi,0)]$ in the unfolded Fermi surface regime[19,28]. The appearance of Γ' at E_F causes the Fermi surface nesting condition to be better in $Y_{0.95}La_{0.05}$1111(T_c=50 K) than the other compounds. This results in the enhancement of AFMSFs for $Y_{0.95}La_{0.05}$1111, that is, T_c increases from 28 K in La1111, to 34 K in $La_{0.8}Y_{0.2}$1111 up to 50 K in $Y_{0.95}La_{0.05}$1111[27,29,30]. According to the spin-fluctuation mediated SC mechanism, the large Fermi surface multiplicity in Ln1111 in addition to the presence of AFMSFs is an another crucial factor for enhancing T_c, which is optimized when the $FeAs_4$ tetrahedron is close to a regular one realized in Ln1111[28]. It is noteworthy that the T dependence of $1/T_1T$ of $(Y_{0.95}La_{0.05})$1111 is saturated below 100 K. A similar saturation and/or broad maximum in $1/T_1T$ was observed for $Ba_{0.6}K_{0.4}Fe_2As_2$ (T_c= 38 K)[31,32], $Ca_4(Mg,Ti)_3Fe_2As_2O_{8-y}$ (T_c= 47 K)[33], and $Sr_4(Mg_{0.3}Ti_{0.7})_2O_6Fe_2As_2$ (T_c=34K)[34], which are characterized by the lattice parameters of the FeAs block being close to the values of the regular tetrahedron. This is in contrast to the T dependence of $1/T_1T$ in $LaFe(As_{1-x}P_x)(O_{1-y}F_y)$ compounds that continues to increase down to T_c as seen in Fig. 8. Likewise, T_c for the Fe-pnictides that reveal a significant enhancement of AFMSFs towards T_c is nearly limited in the compounds within the range from T_c ~10 K to T_c ~30 K. These results suggest that AFMSFs are not always a unique factor to attain T_c=55 K in the Fe-based compounds. In this context, the optimized electronic states for the occurrence of SC in Fe-pnictides is realized for the regular $FeAs_4$ tetrahedron in which the multiorbital fluctuations may play some roles for the onset of SC[35], since the spin and orbital degrees of freedom can be intimately coupled to each other.

V. CONCLUSION

In conclusion, systematic ^{31}P-NMR studies of $LaFe(As_{1-x}P_x)(O_{1-y}F_y)$ have revealed that the antiferromagnetic spin fluctuations at low energies cause a peak at T_c=27 K and at T_c=24 K for y=0.1 and 0.05, respectively. The result indicates that the AFMSFs are responsible for the T_c increase in $LaFe(As_{1-x}P_x)(O_{1-y}F_y)$ as a primary mediator of the Cooper pairing. We highlight that the present studies of the LaFe(As,P)(O,F) series compounds provide clear evidence that the development of AFMSFs enhances T_c even if the present La1111 compounds are far from the AFM ordered phase and optimal lattice parameters. In the T_c=50 K class of Fe-pnictides, however, it should be noted that the AFMSFs do not critically develop down to T_c, instead, they seem to be

saturated. We propose that T_c of Fe-pnictides exceeding 50 K is maximized under an intimate collaboration of the AFMSFs and other factors originating from the optimization of the local structure.

Acknowledgement

We thank K. Kuroki and K. Suzuki for fruitful discussion and comments.

* e-mail address: mukuda@mp.es.osaka-u.ac.jp

[1] Y. Kamihara, T. Watanabe, M. Hirano and H. Hosono, J. Am. Chem. Soc. **130**, 3296 (2008).
[2] H. Luetkens, H.-H. Klauss, M. Kraken, F. J. Litterst, T. Dellmann, R. Klingeler, C. Hess, R. Khasanov, A. Amato, C. Baines, M. Kosmala, O. J. Schumann, M. Braden, J. Hamann-Borrero, N. Leps, A. Kondrat, G. Behr, J. Werner, and B. Büchner, Nat. Mater. **8**, 305 (2009).
[3] Z. A. Ren, W. Lu, J. Yang, W. Yi, X. L. Shen, Z. C. Li, G. C. Che, X. L. Dong, L. L. Sun, F. Zhou, and Z. X. Zhao, Chin. Phys. Lett. **25**, 2215 (2008).
[4] Z. A. Ren, G. C. Che, X. L. Dong, J. Yang, W. Lu, W. Yi, X. L. Shen, Z. C. Li, L. L. Sun, F. Zhou, and Z. X. Zhao, Europhys. Lett. **83**, 17002 (2008).
[5] C. H. Lee, A.Iyo, H. Eisaki, H. Kito, M. T. Fernandez-Diaz, T. Ito, K. Kihou, H. Matsushita, M. Braden, and K. Yamada, J. Phys. Soc. Jpn. **77**, 083704 (2008).
[6] Y. Mizuguchi, Y. Hara, K. Deguchi, S. Tsuda, T. Yamaguchi, K. Takeda, H. Kotegawa, H. Tou, and Y. Takano, Supercond. Sci. Technol. **23**, 054013 (2010).
[7] K. Miyazawa, K. Kihou, P. M. Shirage, C.-H Lee, H. Kito, H. Eisaki, and A. Iyo, J. Phys. Soc. Jpn. **78**, 034712 (2009).
[8] Y. Kamihara, H. Hiramatsu, M. Hirano, R. Kawamura, H. Yanagi, T. Kamiya, and H. Hosono, J. Am. Chem. Soc. **128**, 10012 (2006).
[9] S. Saijo, S. Suzuki, S. Miyasaka, and S. Tajima, Physica C **470**, S298 (2010).
[10] S. Miyasaka, A. Takemori, T. Kobayashi, S. Suzuki, S. Saijo, and S. Tajima, J. Phys. Soc. Jpn. **82**, 124706 (2013).
[11] K. T. Lai, A. Takemori, S. Miyasaka, S. Tajima, A. Nakao, H. Nakao, R. Kumai, and Y. Murakami, to be published in JPS Conf. Proc.
[12] C. Wang, S. Jiang, Q. Tao, Z. Ren, Y. Li, L. Li, C. Feng, J. Dai, G. Cao, and Z. Xu, Europhys. Lett. **86**, 47002 (2009).
[13] S. Suzuki, S. Miyasaka, S. Tajima, T. Kida, and M. Hagiwara, J. Phys. Soc. Jpn. **78**, 114712 (2009).
[14] H.-J. Grafe, D. Paar, G. Lang, N. J. Curro, G. Behr, J. Werner, J. Hamann-Berrero, C. Hess, N. Leps, R. Klingeler, and B. Büchner, Phys. Rev. Lett. **101**, 047003 (2008).
[15] N. Terasaki, H. Mukuda, M. Yashima, Y. Kitaoka, K. Miyazawa, P.M. Shirage, H. Kito, H. Eisaki, and A. Iyo, J. Phys. Soc. Jpn. **78**, 013701 (2009).
[16] T. Imai, K. Ahilan, F. L. Ning, T. M. McQueen, and R. J. Cava, Phys. Rev. Lett. **102** 177005 (2009).
[17] F. Ning, K. Ahilan, T. Imai, A. S. Sefat, R. Jin, M. A. McGuire, B. C. Sales, and D. Mandrus, J. Phys. Soc. Jpn. **78**, 013711 (2009).
[18] H. Ikeda, J. Phys. Soc. Jpn. **77**, 123707 (2008).
[19] K. Kuroki, H. Usui, S. Onari, R. Arita, and H. Aoki, Phys. Rev. B **79**, 224511 (2009).
[20] Y. Shimizu, T. Yamada, T. Takami, S. Niitaka, H. Takagi, and M. Itoh, J. Phys. Soc. Jpn. **78**, 123709 (2009).
[21] Y. Nakai, T. Iye, S. Kitagawa, K. Ishida, H. Ikeda, S. Kasahara, H. Shishido, T. Shibauchi, Y. Matsuda, and T. Terashima, Phys. Rev. Lett. **105**, 107003 (2010).
[22] G. F. Ji, J. S. Zhang, L. Ma, P. Fan, P. S. Wang, J. Dai, G. T. Tan, Y. Song, C. L. Zhang, P. C. Dai, B. Normand, and W. Yu, Phys. Rev. Lett. **111**, 107004 (2013).
[23] Y. Nakai, K. Ishida, Y. Kamihara, M. Hirano, and H. Hosono, J. Phys. Soc. Jpn. **77**, 073701 (2008).
[24] T. Nakano, N. Fujiwara,Y. Kamihara, M. Hirano, H. Hosono, H. Okada, and H. Takahashi, Phys. Rev. B **82**, 172502 (2010).
[25] T. Oka, Z. Li, S. Kawasaki, G. F. Chen, N. L. Wang, and G.-q. Zheng, Phys. Rev. Lett. **108**, 047001 (2012).
[26] F. Hammerath, U. Gräfe, T. Kühne, H. Kühne, P. L. Kuhns, A. P. Reyes, G. Lang, S. Wurmehl, B. Büchner, P. Carretta, and H.-J. Grafe, Phys. Rev. B **88**, 104503 (2013).
[27] H. Mukuda, S. Furukawa, H. Kinouchi, M. Yashima, Y. Kitaoka, P. M. Shirage, H. Eisaki, and A. Iyo, Phys. Rev. Lett. **109**, 157001 (2012).
[28] H. Usui and K. Kuroki, Phys. Rev. B, **84**, 024505 (2011).
[29] H. Yamashita, H. Mukuda, M. Yashima, S. Furukawa, Y. Kitaoka, K. Miyazawa, P. M. Shirage, H. Eisaki, A. Iyo, J. Phys. Soc. Jpn. **79**, 103703 (2010).
[30] H. Mukuda, N. Terasaki, H. Kinouchi, M. Yashima, Y. Kitaoka, S. Suzuki, S. Miyasaka, S. Tajima, K. Miyazawa, P. M. Shirage, H. Kito, H. Eisaki, and A. Iyo, J. Phys. Soc. Jpn. **77**, 093704 (2008).
[31] M. Yashima, H. Nishimura, H. Mukuda, Y. Kitaoka, K. Miyazawa, P. M. Shirage, K. Kiho, H. Kito, H. Eisaki, and A. Iyo, J. Phys. Soc. Jpn. **78**, 103702 (2009).
[32] M. Hirano, Y. Yamada, T. Saito, R. Nagashima, T. Konishi, T. Toriyama, Y. Ohta, H. Fukazawa, Y. Kohori, Y. Furukawa, K. Kihou, C. H. Lee, A. Iyo, and H. Eisaki, J. Phys. Soc. Jpn. **81**, 054704 (2012).
[33] Y. Tomita, H. Kotegawa, Y. Tao, H. Tou, H. Ogino, S. Horii, K. Kishio, and J. Shimoyama, Phys. Rev. B **86**, 134527 (2012).
[34] K. Yamamoto, H. Mukuda, H. Kinouchi, M. Yashima, Y. Kitaoka, M. Yogi, S. Sato, H. Ogino, and J. Shimoyama, J. Phys. Soc. Jpn. **81**, 053702 (2012).
[35] H. Kontani and S. Onari, Phys. Rev. Lett. **104**, 157001 (2010).